

Lithium Recovery from Aqueous Resources and Batteries: A Brief Review

A review of the methods to produce lithium and approaches to recycling from end-of-life lithium-ion batteries

Ling Li

Chemical Sciences Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA

Vishwanath G. Deshmane

Materials Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA

M. Parans Paranthaman*

Chemical Sciences Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA

*Email: paranthamanm@ornl.gov

Ramesh Bhawe

Materials Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA

Bruce A. Moyer

Chemical Sciences Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA

Stephen Harrison

Alger Alternative Energy LLC, Brawley, California 92227, USA

portable electronics. To alleviate the potential risk of undersupply, lithium can be extracted from raw sources consisting of minerals and brines or from recycled batteries and glasses. Aqueous lithium mining from naturally occurring brines and salt deposits is advantageous compared to extraction from minerals, since it may be more environmentally friendly and cost-effective. In this article, we briefly discuss the adsorptive behaviour, synthetic methodology and prospects or challenges of major sorbents including spinel lithium manganese oxide (Li-Mn-O or LMO), spinel lithium titanium oxide (Li-Ti-O or LTO) and lithium aluminium layered double hydroxide chloride (LiCl·2Al(OH)₃). Membrane approaches and lithium recovery from end-of-life LIB will also be briefly discussed.

1. Introduction

Due to the accelerated expansion of the LIB industry, the global demand for lithium is expected to increase significantly with an annual growth rate of 8.9% through 2019 to 49,350 metric tonnes (1–3). The estimated global lithium end-use applications are summarised in **Table I**. Batteries used in portable electronics, hybrid cars and electric vehicles consume ~35% of the total lithium market share. The ceramics and glass sector with a ~32% market share is the second highest consumer of lithium. Primary lithium resources are from pegmatites, continental brines and geothermal brines, and the secondary resources are from clays and seawater (4). Lithium carbonate (Li₂CO₃), which is the major commercial lithium product, is

The demand for lithium is expected to increase drastically in the near future due to the increased usage of rechargeable lithium-ion batteries (LIB) in electric vehicles, smartphones and other

Table I List of Estimated Global Lithium End-Use Applications^a

Applications	Market share, %	Products
Batteries – portable electronics; hybrid cars; electric vehicles; grid storage applications	35	Li ₂ CO ₃ ; LiOH; Li metal; lithium hexafluorophosphate (LiPF ₆) electrolyte salts; lithium chloride (LiCl); Li alloys; lithium cobalt oxide (LiCoO ₂); and other Li electrode compositions
Ceramics and glass	32	Spodumene – LiAl(SiO ₃) ₂ ; Li ₂ CO ₃
Lubricants and greases	9	LiOH
Air treatment; continuous casting mould flux powders; polymer production; primary Al production	5; 5; 4; 1	Li organometallics; Li metal; LiCl; lithium aluminium hydride (LiAlH ₄); butyl lithium; lithium citrate
Other uses such as in medicine as antidepressants, bipolar disorder	9	Li compounds

^a Summarised from (5, 9, 10)

mostly prepared through mining, extracting and treating spodumene ores and salt lake brines (4). Lithium carbonate is losing market share to lithium hydroxide (LiOH), which is increasingly favoured for LIB cathode applications (2). Currently, two brine operations in Chile and a spodumene operation in Australia account for the majority of global lithium production (5).

Extraction from brines would be advantageous relative to extraction from ores, since it is more environmentally friendly and cost-effective (6). It is estimated that the lithium production cost from salt lake brines is US\$2–3 kg⁻¹, whereas that from the ores or spodumene is US\$6–8 kg⁻¹ (4). The major lithium-containing brine resources around the world are listed in **Table II**. The lithium concentration of brines ranges from 100–1000 mg l⁻¹, whereas average lithium concentration present in seawater is merely 0.17 mg l⁻¹ (4). Therefore, salt lake and geothermal brines are the most promising aqueous resources for industrial scale lithium extraction (7). In fact, a majority of lithium is currently produced through solar evaporation, followed by the removal of impurities through precipitation. However, this method is time consuming (usually 18–24 months) and requires large land areas. Besides, the presence of excessive cations such as sodium, potassium, calcium and magnesium plus chloride ions in the brines makes it challenging to obtain a high purity product.

Finally, the rechargeable LIB industry has expanded significantly with the maturation of clean and sustainable energy technologies. A

short review on the recovery of lithium and other valuable metals from end-of-life LIBs are discussed in Section 5.

2. Recovery of Lithium from Brines by Adsorption and Ion Exchange

Spinel Li-Mn-O, spinel Li-Ti-O and LiCl·2Al(OH)₃ have been identified as potential sorbents for lithium extraction from aqueous resources. In the section below, we discuss these sorbents including their synthetic methods, structures, adsorption mechanisms, morphologies and adsorption or ion exchange capacities from different aqueous resources.

2.1 Lithium Manganese Oxides (Li-Mn-O)

Spinel-type Li-Mn-O are attractive candidates for commercial lithium extraction owing to their high capacity and superior selectivity towards lithium. Li-Mn-O are synthesised as precursor materials, from which the ion sieves are obtained by replacing the Li⁺ with H⁺. Li-Mn-O can be synthesised *via* various methods including solid state reaction, sol-gel, hydrothermal or reflux, yielding different particle sizes and morphologies, which lead to different ion exchange capacities of the lithium de-intercalated sorbents. In general, the Li-Mn-O precursors can be expressed by the formula (Li)[Li_xMn_{2-x}]O₄, where A-site (mostly Li) and B-site (Li and/or Mn) represent 8a tetrahedral and 16d octahedral sites

Table II World Brine Compositions^{a,b}

Source	Li, wt%	Na, wt%	Mg, wt%	K, wt%	Ca, wt%
Clayton Valley, USA	0.0163	4.69	0.019	0.4	0.045
Salton Sea, USA	0.01–0.04	5.00–7.00	0.07–0.57	1.30–2.40	2.26–3.9
Salar de Atacama, Chile	0.157	9.1	0.965	2.36	0.045
HombreMuerto, Argentina	0.068–0.121	9.9–10.3	0.018–0.14	0.24–0.97	0.019–0.09
Salar de Uyuni, Bolivia	0.0321	7.06	0.65	1.17	0.0306
Searles Lake, USA	0.0054	11.8	–	2.53	0.0016
Great Salt Lake, USA	0.0018	3.70–8.70	0.5–0.97	0.26–0.72	0.026–0.036
Dead Sea, Israel	0.0012	3.01	3.09	0.56	1.29
Sua Pan, India	0.002	6	–	0.2	–
Bonneville, USA	0.0057	8.3	0.4	0.5	0.0057
Zabuye, China	0.0489	7.29	0.0026	1.66	0.0106
Taijinaier, China	0.031	5.63	2.02	0.44	0.02

^a Adapted from (8, 9)

^b Please note only cations with high concentrations are provided in addition to Li

(10), and the acid treated ion sieves have a general formula of $\text{MnO}_2 \cdot x\text{H}_2\text{O}$. The primary Li uptake mechanism for the spinel-type sorbents is the Li^+/H^+ exchange, in which the Li^+ can be intercalated/de-intercalated into the octahedral interstices, with an intact spinel structure (11). Furthermore, the Li^+ can be cycled in and out freely within a relatively wide range of Li:Mn molar ratios (12, 13), resulting in several common manganese oxide precursors including LiMn_2O_4 (10, 12, 14–18), $\text{Li}_{1.6}\text{Mn}_{1.6}\text{O}_4$ (11, 19–26) and $\text{Li}_{1.33}\text{Mn}_{1.67}\text{O}_4$ (19, 27–32). Desorption/regeneration of the spinel-type sorbents requires contacting the sorbents with acid.

Table III lists the ion exchange properties of the lithium ion sieves derived from Li-Mn-O with various Li:Mn molar ratios. The lithium extraction capacity depends on various parameters including the synthetic condition of the precursor materials (20, 33), actual Li:Mn molar ratio (33), temperature and pH of the contact solution (22). Therefore, the reported ion exchange behaviour of a given sorbent can vary between different research groups. To date, the maximum ion exchange capacity of the manganese oxide is 54.65 mg g^{-1} which was realised recently in $\text{Li}_{1.33}\text{Mn}_{1.67}\text{O}_4$ synthesised from Li_2CO_3 and MnCO_3 (30). The as-prepared $\text{Li}_{1.33}\text{Mn}_{1.67}\text{O}_4$ powders were mixed with a chitosan binder and extruded into cylinder-shaped material (chitosan-LMO, diameter of 0.7 mm). The extraction was carried out in a column system with seawater flowing at

room temperature. Nevertheless, the nano-sized $\text{Li}_{1.33}\text{Mn}_{1.67}\text{O}_4$ prepared by a gel process exhibited a slightly lower lithium uptake of 28.2 mg g^{-1} from artificial seawater (31). In fact, $\text{Li}_{1.33}\text{Mn}_{1.67}\text{O}_4$ prepared from different precursors exhibited different lithium uptake even though the synthetic method and temperature are exactly the same (27). A comparative study showed that ion sieves derived from $\text{Li}_4\text{Mn}_5\text{O}_{12}$ ($\text{Li}_{1.33}\text{Mn}_{1.67}\text{O}_4$) exhibited a higher capacity compared to those derived from LiMn_2O_4 (46.6 mg g^{-1} vs. 23.9 mg g^{-1}) (10).

LiMn_2O_4 related ion sieve has a relatively lower ion exchange capacity and weak stability due to the Jahn-Teller distortion with cycling. The MnO_2 preparation was first reported in 1981 *via* treating LiMn_2O_4 with acid (34). It was further confirmed in 1984 that lithium can be cycled in and out of the $[\text{Mn}_2]\text{O}_4$ framework over a wide range of x to form $\text{Li}_{1-x}\text{Mn}_2\text{O}_4$ (12). The acid treated ion sieve MnO_2 obtained from LiMn_2O_4 nanowire exhibited an ion exchange capacity of $\sim 16.8 \text{ mg g}^{-1}$ from LiCl solutions (15). In later years, the same research group synthesised LiMn_2O_4 nanorods (15–20 nm in diameter and several micrometers in length) *via* a one-step soft chemistry method, and the related ion sieve showed a slightly higher extraction capacity of 20.5 mg g^{-1} from LiCl solutions (14).

$\text{Li}_{1.6}\text{Mn}_{1.6}\text{O}_4$ related ion sieve $\text{MnO}_2 \cdot 0.5\text{H}_2\text{O}$ has an overall relatively high capacity, which is attributed to the availability of strong acidic sites

Table III List of Some Common Li-Mn-O Precursors Synthesised Under Different Conditions

Precursors	Synthesis	Morphology	Solution	Capacity, mg g ⁻¹	Ref.
H_{1.33}Mn_{1.67}O₄ H_{1.6}Mn_{1.6}O₄	-	-	pH = 6.6	27-30	(19)
	400°C using lithium nitrate (LiNO ₃) as a flux from different precursors	Various	-	47.1 (optimum)	(27)
	Low-temperature solid-phase reaction (673 K)	Nanorod	Mixed solution with Li ⁺ , Na ⁺ , K ⁺ , Mg ²⁺ and Ca ²⁺ of 10.0 mmol l ⁻¹	46.6	(10)
	A combination of hydrothermal reaction and solid-phase calcinations	Spherical with 2-3.5 μm in diameter, polyvinyl chloride (PVC)-manganese(IV) oxide (MnO ₂)	LiCl, pH = 10.1	23.5	(35)
Li_{1.33}Mn_{1.67}O₄	Tartaric acid gel process with lithium acetate (CH ₃ COOLi) and Mn(CH ₃ COO) ₂ ·4H ₂ O	Nano	Artificial seawater	28.2	(31)
	Solid state	Cylinder-shaped, chitosan-LMO granules diameter of 0.7 mm	Seawater through a column setup packed with chitosan-LMO, room temperature, pH = 6.6	54.7	(30)
	Modelling a column system	-	-	-	(28)
	Controlled low-temperature hydrothermal synthesis	Nanowire with 5 nm diameter and 400 nm in length	LiCl, pH = 9.19	16.8	(15)
LiMn₂O₄	Manganese(II) nitrate tetrahydrate (Mn(NO ₃) ₂), LiOH and hydrogen peroxide (H ₂ O ₂) mixed solution at 383 K for 8 h	MnO ₂ nanorods with 15-20 nm in diameter	LiCl (10.0 mmol l ⁻¹ Li ⁺), pH = 10.1	20.5	(14)
	High-temperature calcinations (1003 K)	Nanorod	Mixed solution with Li ⁺ , Na ⁺ , K ⁺ , Mg ²⁺ and Ca ²⁺ of 10.0 mmol l ⁻¹	23.9	(10)
Molar Mn/Li = 1.125 Li_{1.6}Mn_{1.6}O₄	Citrate method	Meso- or macroporous foam	Lithium-enriched salt lake brine (pH = 6; main metallic ions: Li ⁺ 237 mg l ⁻¹ , Na ⁺ 3591 mg l ⁻¹ , K ⁺ 3118 mg l ⁻¹ and Mg ²⁺ 109 g l ⁻¹)	1.5	(36)
	Sol-gel with Mn(NO ₃) ₂ and LiOH	One-dimensional (1D) nanowire	Saltern bittern, pH = 10	10.5	(21)

Continued

Precursors	Synthesis	Morphology	Solution	Capacity, mg g ⁻¹	Ref.
Molar Mn/Li = 1.125	Calcination of lithium manganese dioxide (LiMnO ₂) which was made by hydrothermal and reflux methods	Materials prepared by the reflux method was less crystalline as compared to the hydrothermal method	Seawater (0.17 mg l ⁻¹ Li ⁺)	40	(20)
	Calcination of LiMnO ₂ which was made by a hydrothermal method using manganese(III) oxide (Mn ₂ O ₃) and LiOH	Particle size 100–300 nm	Simulated brine (270 mg l ⁻¹ Li ⁺), 50°C, pH = 5.35	27.2	(22)
Li_{1.6}Mn_{1.6}O₄ Li_{1.16}Sb_{0.29}Mn_{1.54}O₄	Calcination of LiMnO ₂ which was made by a hydrothermal method using potassium permanganate (KMnO ₄), manganese(II) chloride (MnCl ₂) and LiOH	Particle size ≤200 nm	LiCl (69.4 mg l ⁻¹ Li ⁺ , with the presence of Na ⁺ , K ⁺ , Ca ²⁺ and Mg ²⁺), pH = 10.1	42.1	(24)
	Calcination of LiMnO ₂ which was made by a controlled redox precipitation using manganese(II) hydroxide (Mn(OH) ₂), LiOH and ammonium persulfate ((NH ₄) ₂ S ₂ O ₈)	Particle size ≤200 nm	Qarhan salt lake brine (179 mmol l ⁻¹ Li ⁺ , 15,190 mmol l ⁻¹ Na ⁺ , 13,729 mmol l ⁻¹ K ⁺ , 429 mmol l ⁻¹ Ca ²⁺ , 80,125 mmol l ⁻¹ Mg ²⁺)	26.9	(25)
	Wet chemistry and hydrothermal at 120°C		LiCl enriched seawater (5 mg l ⁻¹ Li ⁺)	40	(37)

inside the solid (20). Li_{1.6}Mn_{1.6}O₄ is relatively difficult to synthesise, usually by calcination of LiMnO₂ in O₂ at an appropriate temperature (8LiMnO₂ + 2O₂ → 5Li_{1.6}Mn_{1.6}O₄). To date, the highest reported ion exchange capacity is 42.1 mg g⁻¹ (6.06 mmol g⁻¹) from LiCl solution at a pH of 10.1 (24). However, the lithium uptake of the same sorbent from salt lake brine dropped to 28.3 mg g⁻¹ (4.08 mmol g⁻¹) and was further reduced to 25.1 mg g⁻¹ after six cycles (24). In addition, the ion exchange capacity increases with increasing stacking fault concentrations in the precursor LiMnO₂ (24, 38). Li_{1.6}Mn_{1.6}O₄ prepared by the hydrothermal method showed a slightly higher lithium uptake and cycling stability than that prepared by the reflux method (20). Lithium extractive materials prepared with LiOH·H₂O and manganese(II) carbonate (MnCO₃) usually have higher Li⁺ ion exchange capacity than materials prepared with Li₂CO₃ and MnCO₃, and an ascending

trend was found in Li⁺ uptake with increasing Li:Mn molar ratio (33). Furthermore, the extraction capacity of Li_{1.6}Mn_{1.6}O₄ in simulated brines (270 mg l⁻¹ Li⁺) increases with increasing temperature (30–50°C) and increasing pH values (1–12) (22). The high selectivity for lithium ions was confirmed, with high separation coefficients of α_{Li/Mg} = 109.5, α_{Li/Na} = 220.7, α_{Li/K} = 125.5 (22).

In addition, there have been studies on ion sieves derived from antimony (37), Mg (39, 40) and Fe (41) doped Li-Mn-O. The ion exchange capacity (from Li⁺ enriched seawater) of ion sieves derived from Li_{1.16}Sb_{0.29}Mn_{1.54}O₄ reached 40 mg g⁻¹ (37). Mg-doped spinel Li-Mn-O ion sieve exhibited an optimum ion exchange capacity of 37.4 mg g⁻¹ from LiCl solution (200 mg l⁻¹ Li⁺, pH = 12) (39). Nevertheless, MgMn₂O₄ exhibited a small ion exchange capacity (from seawater) of 8.5 mg g⁻¹ and the equilibrium time is 96 hours, indicating a slow ion exchange (42).

In summary, Li-Mn-O ion sieves exhibited a high ion exchange capacity and high selectivity for lithium ions from various aqueous resources. The acid generated during lithium uptake can be recycled for regenerating the sorbents. This could potentially reduce the cost of the acid consumption itself. However, the dissolution of Mn^{2+} during the regeneration process with acid degrades the ion exchange capacity and results in a poor cycling stability. This key issue seriously limits Li-Mn-O's potential for upscaling. Further studies are needed to improve the stability during cycling to realise a stable ion exchange capacity. Simplicity of the regeneration process is also desirable.

2.2 Lithium Titanium Oxides (Li-Ti-O)

Titanium-based spinel oxides share most of the advantages with the manganese-based spinel oxides, with an addition of being more environmentally friendly, as the titanium is an earth abundant element, is stable and does not dissolve in acid. In particular, metatitanic acid (H_2TiO_3) has been considered as an emerging environmentally friendly sorbent for lithium extraction from aqueous resources. The precursor lithium titanate (Li_2TiO_3) was first synthesised in 1988 and various synthesis methods are now available in the literature, including solid-state reaction (43–47), hydrothermal (48) and sol-gel (49, 50).

Debate persists about the crystal structures of Li_2TiO_3 and H_2TiO_3 , in which Chitrakar *et al.* (43) indexed both compounds as monoclinic with a space group $C2/c$, but later Yu *et al.* (51) pointed out that H_2TiO_3 should be more reasonably indexed with the $3R_1$ space group with an LDH structure. Typically, layered H_2TiO_3 , derived from a layered Li_2TiO_3 precursor upon treatment with HCl solution, will go through ion exchange with lithium ions from the geothermal brines at a pH >7 to form Li_2TiO_3 ($\text{H}_2\text{TiO}_3 + 2\text{LiOH} \rightarrow \text{Li}_2\text{TiO}_3 + 2\text{H}_2\text{O}$). Lithium can be recovered from Li_2TiO_3 by treating with HCl solution ($\text{Li}_2\text{TiO}_3 + 2\text{HCl} \rightarrow \text{H}_2\text{TiO}_3 + 2\text{LiCl}$). The theoretical ion exchange capacity of H_2TiO_3 is up to 142.9 mg g^{-1} (48), whereas the highest experimental ion exchange capacity so far is 94.5 mg g^{-1} (46). This is actually the maximum achievable capacity, as only 75% of the H^+ occupied ion exchange sites in H_2TiO_3 are exchangeable with Li^+ (44). **Table IV** summarises the adsorptive behaviours of H_2TiO_3 synthesised under different conditions from various research groups.

It was first demonstrated in 2014 that H_2TiO_3 exhibits an extremely high selectivity toward lithium

ions in the sodium bicarbonate (NaHCO_3)-added salt brine and the ion exchange capacity reached 32.6 mg g^{-1} at a pH of 6.5 (43). However, the ion exchange rate is slow, taking 24 hours to get to equilibrium. This work has since stimulated great efforts investigating the ion exchange behaviour of this emerging ion sieve (44–49, 52, 53). The isotherm of H_2TiO_3 exhibited a Langmuir type behaviour, following the pseudo-second-order rate model (45, 46). The ion exchange capacity of H_2TiO_3 increases with increasing Li^+ concentration and decreasing pH values of the aqueous resources (46, 49). Specifically, the ion exchange capacity of H_2TiO_3 increased from 11.26 to 31.27 mg g^{-1} when initial concentration of Li^+ was increased from 500 to 2500 ppm (pH = 13.46) (49). To further elucidate the effects of other factors on the ion exchange capacity of H_2TiO_3 , a comprehensive orthogonal test with five factors (pre-calcination temperature, Li:Ti molar ratio, reaction temperature, ion exchange temperature, Li^+ concentration) was performed (52). The highest ion exchange capacity of 57.8 mg g^{-1} is achieved under the optimum conditions: Li^+ concentration = 4.0 g l^{-1} (highest among the tested), ion exchange temperature = 60°C (highest among the tested), molar ratio of Li:Ti = 2.2, reaction temperature = 650°C , pre-calcination temperature = 25°C . To make H_2TiO_3 more economically efficient, low-grade titanium slag was used as the starting material and the optimal capacity reached 27.8 mg g^{-1} (47).

$\text{Li}_4\text{Ti}_5\text{O}_{12}$ is one of the common anode materials used in LIB (54) and the related $\text{H}_4\text{Ti}_5\text{O}_{12}$ is a common ion sieve for lithium extraction from aqueous solutions. $\text{H}_4\text{Ti}_5\text{O}_{12}$ derived from $\text{Li}_4\text{Ti}_5\text{O}_{12}$ nanotubes ($\sim 70 \text{ nm}$ in diameter) exhibited an ion exchange capacity of 39.43 mg g^{-1} from LiCl solution ($120 \text{ mg l}^{-1} \text{ Li}^+$, pH = 9.17). In summary, H_2TiO_3 is an attractive sorbent for selective lithium extraction with superior advantages including high ion exchange capacity, high selectivity, high stability, environmental friendliness and economic efficiency. However, it is still at the laboratory scale, partly due to the acid requirement during the regeneration process, which produces secondary wastes.

2.3 Lithium Aluminium Layered Double Hydroxide Chloride

While the Li-Mn-O and Li-Ti-O sorbents have attracted significant attention from academia, $\text{LiCl}\cdot 2\text{Al}(\text{OH})_3\cdot x\text{H}_2\text{O}$ (referred to as Li/Al LDH) is an attractive candidate for application in large scale

Table IV List of the Adsorptive Properties of H₂TiO₃ Synthesised Under Different Conditions

Synthesis Method	Ion sieve morphology	Solution	Capacity, mg g ⁻¹	Ref.
Solid state	Uniform particle, 1–2 μm	LiOH (694.1 mg l ⁻¹ Li ⁺)	39.8	(45)
Solid state	Plate like particles with average diameter of 100–200 nm	Li enriched salt lake brine (1630 mg l ⁻¹ Li ⁺ , collected from Salar de Uyuni, Bolivia) added with sodium bicarbonate (NaHCO ₃), pH = 6.5	32.6	(43)
Solid state using titanium dioxide (TiO₂) and LiOH·H₂O	–	LiOH (2.0 g l ⁻¹ Li ⁺), 25°C	39.2	(44)
Sol-gel	Particles size ranges from 20–70 nm	LiOH (4.0 g l ⁻¹ Li ⁺), 60°C	Optimum 57.8	(52)
Low grade Ti, solid state	100–300 nm	LiOH (2.0 g l ⁻¹ Li ⁺)	27.8	(47)
Solid state 700°C	Plate-like particle, 100–300 nm	LiOH+LiCl	94.5	(46)
Solid state	H ₂ TiO ₃ mixed with poly(vinyl alcohol) (PVA) matrix, porous composite foam	Seawater pH = 7.64	30.3	(53)
Solid state from LiOH·H₂O and TiO₂	Plate-like particle	LiOH (2.0 g l ⁻¹ Li ⁺)	76.7	(48)
Sol-gel using CH₃COOLi and Ti(OC₄H₉)₄	60–80 nm	LiOH (4.0 g l ⁻¹ Li ⁺)	Optimum, 27.4	(49)

industrial plants due to its various advantages, including low cost, environmental friendliness and easy regeneration. Li/Al LDH materials have a general formula [LiAl₂(OH)₆]⁺B⁻·nH₂O, where B = Cl, Br. They are crystallised in hexagonal symmetry with the Li⁺ located in the vacant octahedral sites within the aluminium hydroxide (Al(OH)₃) layer (55). The [LiAl₂(OH)₆]⁺ layers are separated by water molecules and hydroxide ions (55). Li/Al LDHs can be synthesised by intercalating the Li⁺ (in the form of LiCl, LiOH, lithium sulfate (Li₂SO₄)) into aluminium hydroxides, which are in the form of naturally occurring minerals such as gibbsite (α-Al(OH)₃) or bayerite (β-Al(OH)₃) (55–59). Recently, alternative synthetic routes such as a solvent-free mechanochemical method have been demonstrated (60, 61).

To the best of our knowledge, there exist limited articles in the literature discussing the adsorptive properties of Li/Al LDH. It was first discovered to be a selective sorbent for lithium extraction by Dow Chemical Inc in 1980 (62). The synthesis method was later modified, leading to an increase in the molar fraction of LiX in LiX/Al(OH)₃ from 0.2 to 0.33 (63). Commercial granular Li/Al LDH

(atomic ratio Li:Al ~0.38) was used in a large scale column system packed with 25 tonnes of sorbent for selective lithium extraction from magnesium-containing brines for more than 200 cycles, demonstrating the good stability of this sorbent (64). Li/Al LDH has a good selectivity for LiCl (the form of Li salts in brine and seawater) compared to other cations, because the distance between Al(OH)₃ layers is at the nanoscale such that only ions with small radii can be intercalated (64). Even though the ionic radii of Mg²⁺ (0.074 nm) and Li⁺ (0.068 nm) are close, the large polarisability of the Li–Cl bond as compared to the Mg–Cl bond still makes this sorbent Li⁺ selective (64).

Simbol Inc, USA (65) developed a column system packed with Li/Al LDHs for the extraction of lithium salts from geothermal brines sourced from the Salton Sea, California, USA. The geothermal brine has a bulk composition of about 260 ppm Li⁺, 63,000 ppm Na⁺, 20,100 ppm K⁺, 33,000 ppm Ca²⁺ and other ions (65). The Li/Al LDHs Simbol Inc prepared have a high Li:Al atomic ratio of up to 0.5, which maximises the number of lithium sites available in the layered structure for the intercalation and de-intercalation of lithium from a brine solution

(65). Note that this invention of extraction process is applicable to geothermal brine as well as other brine sources. Recently, Li *et al.* demonstrated safe LIB using $\text{Li}_4\text{Ti}_5\text{O}_{12}$ (LTO) electrode materials prepared from Li_2CO_3 extracted from geothermal brine solutions using Li/Al LDH sorbents with good cyclability (65). These demonstrations provide a promising way for making low cost, large scale LTO electrode materials for energy storage applications. In summary, $\text{LiCl}\cdot 2\text{Al}(\text{OH})_3\cdot x\text{H}_2\text{O}$ is an attractive candidate to be applied in large scale plant for extraction of lithium salts from various brines. A detailed study on this sorbent regarding the isotherms is still needed.

3. Recovery of Lithium from Brines by Membranes

Membrane processes offer several advantages compared to conventional processes, such as lower energy requirements and capital investments, simple and easy to operate systems, smaller footprints, ease of scalability and many other specific application related advantages. For example, in sorbent based separations in packed and fluidised bed systems, there is a significant pressure drop and loss of sorbent particles. However, both these limitations can be eliminated by the fabrication of mixed matrix membranes including Li^+ selective sorbent. Although there is an increasing interest in membrane based Li^+ recovery processes, there are only limited published reports discussing techniques such as nanofiltration (2, 5, 21, 66–69), electrolysis (70–72), electrodialysis (73–76), dialysis (74), membrane solvent extraction (77–79) and membrane type adsorbents or mixed matrix membranes (80–84). The summary of these studies is provided in **Table V**.

The first study on the application of nanofiltration for the recovery of lithium from brines used a spiral-wound Desal-5 DL 2540C membrane (GE Osmonics), which showed a 61–67% retention of the Mg^{2+} , while Li^+ passed through the membrane, giving a $\text{Li}^+/\text{Mg}^{2+}$ separation factor of 3.5 (66). A Desal-DK membrane (GE Osmonics) showed a $\text{Li}^+/\text{Mg}^{2+}$ separation factor ranging between 2 to 3.2 depending upon the feed Li^+ and Mg^{2+} concentration and their ratio (5, 68). The higher operating pressure, lower pH and higher feed $\text{Li}^+:\text{Mg}^{2+}$ ratio improved the separation (68). The relative Li^+ separation performance of nanofiltration-NF90 (Dow) and low pressure reverse osmosis-XLE (Dow) membranes was evaluated with salt lake brine (2). NF90 membrane appeared more efficient, showing 100%

Mg^{2+} rejection compared to only 15% for Li^+ , which was attributed to its higher hydraulic permeability to pure water and 0.1 M sodium chloride (NaCl) solution, and its lower critical pressure. Recently, novel positively charged polyamide composite nanofiltration membranes were fabricated by the interfacial polymerisation of DAPP and TMC and supported on PAN ultrafiltration hollow fibre membrane (21). The advantage of using hollow fibre compared to the mostly reported flat-sheet configuration is that the hollow fibres have high packing density, lower energy and maintenance cost and easy fabrication of the modules. The rejection order of this composite hollow fibre membrane was magnesium chloride (MgCl_2) > magnesium sulfate (MgSO_4) > NaCl \geq LiCl (21).

Functionalisation of the positively charged membrane (fabricated by interfacial polymerisation of TMC and BPEI supported on polyetherimide sheets) with EDTA showed good separation performance with a $\text{Li}^+/\text{Mg}^{2+}$ separation factor of ~ 9.2 . This was attributed to the tendency of EDTA to form complexes with the divalent cations. It was suggested that the combination of Donnan exclusion, dielectric exclusion and steric hindrance governed the mass transport inside the nanofiltration membranes. Furthermore, it was also indicated that when membrane pore size is close to the ionic radius, steric hindrance plays a significant role in the separation (21, 66, 67).

An electrolysis method employing the typical anion exchange membranes (MA-7500, SYBRON and American IONAC[®]) and lithium iron phosphate (LiFePO_4)/iron(III) phosphate (FePO_4) electrodes was investigated for the extraction of Li^+ from salt lake brines (70–72). The effect of different parameters on the Li^+ extraction performance was studied. At optimised operating conditions, electrodes exhibited a noteworthy Li^+ exchange capacity of 38.9 mg g^{-1} (72).

Recovery of lithium from seawater was also demonstrated by an electrodialysis based technique, which uses organic membranes impregnated with an ionic liquid (73, 75). The separation of lithium was mainly achieved based on its relatively lower or higher permeation rates compared to other cations. However, it was suggested that the poor durability of the ionic membrane is a major issue preventing long-term lithium recovery (74). The applied voltage, feed velocity, feed $\text{Li}^+:\text{Mg}^{2+}$ ratio and pH significantly influenced the $\text{Li}^+/\text{Mg}^{2+}$ separation factor (76).

Supported liquid membranes (SLMs) have also attracted interest, borrowing selectivity from

Table V Summary of Reported Studies of Lithium Extraction Using Membrane Processes

Mechanism or separation process	Lithium source	Membrane system	Separation factor	Ref.
Nanofiltration	Salt lake brine	Spiral-wound Desal-5 DL 2540C, spiral-wound Desal DK (GE Osmonics, USA); NF90 and XLE (Dow, USA); Spiral-wound DK-1812 (Suntar Membrane Tech, China), DL-2540; 1,4-bis(3-aminopropyl)piperazine (DAPP) and trimesoyl chloride (TMC) polymerised on the polyacrylonitrile (PAN) hollow fibre; ethylenediaminetetraacetic acid (EDTA) functionalised TMC and branched polyethyleneimine (BPEI)	Li ⁺ /Mg ²⁺ : 2–42	(2, 5, 21, 66–69)
Electrolysis, electro dialysis, dialysis	Salt lake brine, seawater	Anion exchange MA-7500 (SYBRON); Selemion™ CMV with ionic liquid TPA-TFSI; Gore-Tex® impregnated with ionic liquid (PP13-TFSI); Li ion conductive glass-ceramics (Ohara Inc, Japan), ACS (Anion exchange) and CIMS (Cation exchange) (ASTOM, Japan)	Highly selective recovery of Li ⁺ , Li ⁺ /Mg ²⁺ : 12–77	(72–76)
Membrane solvent extraction	Geothermal water, salt lake brine	α -acetyl- <i>m</i> -dodecylacetophenone (LIX54) and tri- <i>n</i> -octylphosphine oxide (TOPO) in kerosene embedded in Celgard® 2500 membrane; tributylphosphate (TBP) + FeCl ₃ in kerosene with polyethersulfone (PES) and sulfonated poly(phthalazinone ether sulfone ketone) (SPPEsk) blend; TBP + iron(III) chloride (FeCl ₃) in kerosene with poly(ethylene-co-vinyl alcohol) (EVAL)	>90% extraction of Li ⁺ in 2 h, high Li ⁺ selectivity	(77–79)
Grothuss	Binary mixtures of Na ⁺ , K ⁺ and Mg ²⁺ with Li ⁺ *	PSS threaded HKUST-1 metal-organic framework (MOF)	Li ⁺ /Na ⁺ : 35, Li ⁺ /Mg ²⁺ : 1815	(80)
Sorption	Seawater, geothermal brine	Li _{1.33} Mn _{1.67} O ₄ /PVC, Li _{1.33} Mn _{1.67} O ₄ encapsulated in polysulfone (PSf)/Kintex, Li _{1.33} Mn _{1.67} O ₄ /PSf/PAN mixed matrix (nanofibre), LDH-polyvinylidene fluoride (PVDF)/PVDF hollow fibres	>90% Li ⁺ recovery, complete Li ⁺ selectivity	(81–85)

the incorporated solvent extraction reagents. Ma *et al.* (77) reported the first study on the extraction of lithium from geothermal water with the SLM technique. A mixture of extractants consisting of LIX54 (the main component is α -acetyl-*m*-dodecylacetophenone) and TOPO were immobilised in the Celgard® 2500 membrane having 37–48% porosity. The SLM showed 95% extraction of Li⁺ in just 2 hours; however, it exhibited stable performance for only up to 72 hours before the flux dropped drastically. The decreased stability was attributed to the pressure difference over the membrane sheet, the solubility of the liquid membrane in the adjacent solutions and emulsion formation of the liquid membrane in aqueous solutions (77).

To improve the stability of the SLM for Li⁺ extraction, a nanoporous ion exchange membrane was fabricated by blending PES with sulfonated poly(phthalazinone ether sulfone ketone) (SPPEsk) as a extractant stabiliser (79). With PES/SPPEsk blend membrane and TBP and FeCl₃ mixed in kerosene as an extractant, Li⁺ extraction was performed both in a single-stage extraction and a sandwiched membrane extraction contactor system. The best Li⁺ extraction performance was obtained at a PES:SPPEsk ratio of 6:4 and a polymer concentration of 30 wt%. However, these membranes had limited stability in benzene and toluene despite being stable in kerosene (78, 79). To further improve the stability of the membrane with different solvents, EVAL membranes were

fabricated. These membranes showed exceptional stability in Li^+ extraction with TBP/ FeCl_3 /kerosene for about 1037 hours. This higher stability was attributed to the unique structure of EVAL, consisting of both hydrophobic ethylene and hydrophilic vinyl alcohol units (78).

In a recent study, novel polystyrene sulfonate (PSS) incorporated HKUST-1 MOF membranes were fabricated for Li^+ recovery from brines through an *in situ* lithium confinement process (80). These MOF membranes showed exceptionally good performance in Li^+ recovery with separation selectivities (molar) of 35, 67 and 1815 over Na^+ , K^+ and Mg^{2+} , respectively. It was established that the perm-selectivity followed a trend of $\text{Li}^+ > \text{Na}^+ > \text{K}^+$, which was determined by the corresponding binding affinities of these cations to the sulfonate groups. The transportation of Li^+ through the membrane is proposed to be governed by the Grotthuss mechanism, wherein the charge is transported by the coordinated hopping of Li^+ between sulfonate groups of PSS threaded through the cavities of HKUST-1 (80). Another successful membrane-type adsorbent of spinel manganese oxide ($\text{H}_{1.33}\text{Mn}_{1.67}\text{O}_4$) was prepared by a solvent exchange method using PVC as a binder (81). This membrane-type adsorbent has an uptake capacity of $10.6 \text{ mg g}^{-1} \text{ Li}^+$ from seawater ($0.17 \text{ mg l}^{-1} \text{ Li}^+$).

A membrane reservoir system with encapsulated $\text{Li}_{1.33}\text{Mn}_{1.67}\text{O}_4$ in PSf and Kimtex (Korea Non-woven Tech Ltd, South Korea) was tested for Li^+ recovery from seawater. The Kimtex based systems showed best results with $\sim 84\%$ Li^+ recovery in one day due to the easy wetting and water penetration in the reservoir (82). The $\text{Li}_{1.6}\text{Mn}_{1.6}\text{O}_4$ -PSf/PAN-based composite mixed matrix nanofibres as a flow through membrane Li^+ absorber was highly permeable to water under minimal trans-membrane pressure (83, 84). The balance between kinetic and dynamic Li^+ adsorption capacity could be obtained at optimal seawater and membrane contact time (84).

Bhave *et al.* (85) have fabricated novel LDH (LIS)/Kynar[®]-PVDF mixed matrix membranes supported on PVDF hollow fibres (Arkema Inc, France) for Li^+ recovery from geothermal brines. Due to the high temperature of the geothermal brines, robust membranes are required to operate at temperatures up to 95°C . Preliminary results showed the potential of these membranes to obtain a high lithium separation factor with nearly complete rejection of other monovalent and divalent cations in the brine solution. The selective sorption/diffusion of Li^+ and back-extraction into

the strip is carried out simultaneously, eliminating the need to employ a separate step for Li^+ recovery.

In summary, although there are many published reports on membrane-based separation processes for lithium extraction, the technology is currently at the laboratory scale with significant potential for further development and process scale-up in the future.

4. Recovery of Lithium from Brines by Other Methods

There have been reports of lithium extraction using other methods such as precipitation and solvent extraction. The precipitation method was used to extract lithium from the Dead Sea in 1981 (86). Later a two-stage precipitation process was developed to extract Li_2CO_3 from brines collected from Salar de Uyuni, Bolivia ($700\text{--}900 \text{ mg l}^{-1} \text{ Li}^+$) (8). Solvent extraction has been widely used to extract metals from the aqueous phase due to the simplicity of the equipment and operation. In fact, it was applied to extract lithium from aqueous solutions of alkali metal salts as early as 1968 (87). The extraction of Li^+ ions into the organic phase is associated with the cation exchange mechanism. Various solvents including tri-*n*-butyl phosphate (88), ionic liquid added 1-ethyl-3-methylimidazolium bis(trifluoromethylsulfonyl)imide ($[\text{C}_2\text{mim}][\text{NTf}_2]$) mixed with tri-*n*-butyl (89) and so on, have been reported for lithium extraction. Organophosphorus ligands in the presence of ammonia were tested for lithium extraction, in which the highest extraction percentages in the presence of H-PHO, H-PHI and H-BIS ligands were 43.2%, 45.7% and 90.0%, respectively (90).

5. Recovery of Lithium from Recycled Lithium-Ion Batteries

A rechargeable LIB mainly comprises a lithium-containing oxide cathode, an anode, an organic electrolyte and a separator. **Table VI** lists the chemical composition of a typical LIB. The cathode is usually made of LiCoO_2 , lithium nickel dioxide (LiNiO_2) and lithium manganese(III,IV) oxide (LiMn_2O_4) and the anode is typically graphite. Aluminium and copper are used as current collectors. The recoverable materials from an end-of-life battery include aluminium, copper, LiOH or Li_2CO_3 , cobalt oxide, nickel oxide and manganese oxide. There have been a number of articles in the literature focused on recovery of metals such as cobalt, lithium and nickel from spent LIBs (91–95).

Table VI Chemical Composition of a Typical LIB^a

Component	wt%
LiCoO ₂	27.5
Steel/Ni	24.5
Cu/Al	14.5
Carbon	16
Electrolyte	3.5
Polymer	14

^a Adapted from (95)

Processes to recycle LIBs were first developed for the sake of environmental considerations, since the waste is usually flammable and toxic. It can also achieve some economic benefits as driven by the prices of cobalt and possibly lithium, though they fluctuate drastically depending on their availability.

Figure 1 presents a flow sheet of a typical hydrometallurgical process, which is the most common process to recover lithium from spent LIBs. The whole procedure involves physical and chemical processes to complete the following steps:

- (a) pretreatment of the spent LIBs – dismantling the cells, thermal treatment and mechanochemical process
- (b) dissolution and leaching of metals from the cathode material with hydrochloric acid (HCl), bioleaching
- (c) separation of lithium and other metals *via* solvent extraction, chemical precipitation and electrochemical process (96–99).

For example, a three-step process (100) was developed to recover cobalt and lithium from the cathode materials:

- (a) leaching of the cathode materials with HCl
- (b) separation of cobalt from lithium with solvent extraction
- (c) precipitation of lithium as carbonate.

Employing the same technique, with organic citric acid as the leachant, 90% cobalt and 100% lithium were recovered from end-of-life LIBs (101). Alkaline solution was used to leach the battery’s internal substances followed by dissolving the residue in sulfuric acid (H₂SO₄) solution, yielding Li₂CO₃ (102). The effect of different parameters such as the concentration of the leachant H₂SO₄, temperature, pulp density and reductant H₂O₂ concentration on the leaching of the waste was investigated (103). An optimum condition of pulp density, 100 g l⁻¹, 2M H₂SO₄, 5 vol% of H₂O₂, with a leaching time of 30 min and a temperature of 75°C, was identified (103). Very recently, several methods to recover lithium and other high value metals such as cobalt from spent LIB have been reported (104–110). From both the viewpoints of environmental friendliness and economic benefits, recovery of lithium from spent LIB is desirable. Nevertheless, most of the recycling processes are still at laboratory scale and much effort needs to be directed into this area. In addition, safety precautions should be emphasised when LIB are dismantled.

Summary and Outlook

Aqueous lithium mining of continental brines appears to be a promising approach to realise economically

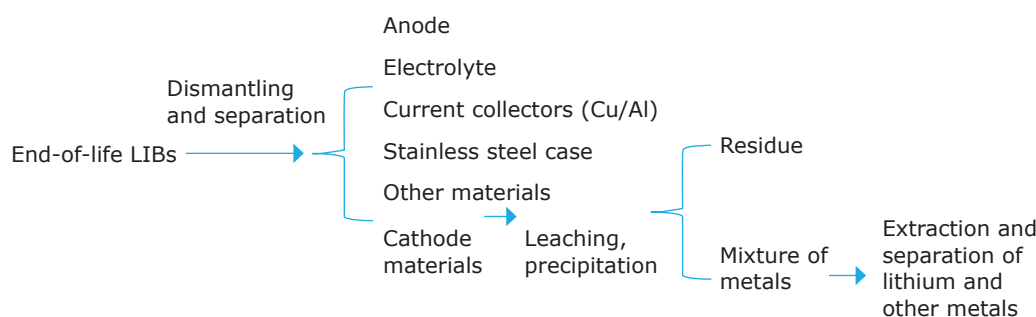


Fig. 1. Flow sheet of a typical recycling process for spent LIBs

and environmentally attractive lithium production. Extraction from seawater would be relatively costly due to the extremely low lithium concentration of 0.17 ppm, though it would be of interest in coastal countries that have neither mineral nor continental brine resources. Alternatively, brines such as salt lake brines or geothermal brines serve as a rich resource. However, evaporation is a slow process that takes up to 24 months and the final products usually have low purity, whereby sorbents and membranes are effective alternatives. The spinel-type sorbents exhibit excellent ion exchange capacity and high selectivity, although the regeneration process could be expensive. On the other hand, $\text{LiCl}\cdot 2\text{Al}(\text{OH})_3$ offers moderate capacity, but this material has other advantages such as low cost and easy regeneration, which are essential for industrial applications. Further research needs to be carried out to better control the defects of the spinel precursor materials. Alternative methods such as solvent extraction could be used to extract lithium from salt lake brines or geothermal brines. The need for large quantities of lithium domestic supply in the USA remains a key priority, for example. Scale-up trials are essential to realise industrial operations to meet the US domestic demand. This requirement justifies continued investment in the extraction of critical lithium from salt lake and geothermal brines. In addition, recovery of lithium from recycled LIB needs a major investment in the near future.

Acknowledgement

This work was supported by the Critical Materials Institute, an Energy Innovation Hub funded by the US Department of Energy, Office of Energy Efficiency and Renewable Energy and Advanced Manufacturing Office.

Additional Information

This manuscript has been authored by UT-Battelle, LLC under Contract No. DE-AC05-00OR22725 with the US Department of Energy (DOE). The United States Government retains and the publisher, by accepting the article for publication, acknowledges that the US Government retains a non-exclusive, paid-up, irrevocable, world-wide license to publish or reproduce the published form of this manuscript or allow others to do so, for US Government purposes. The DOE will provide public access to these results of federally sponsored research in accordance with the

DOE Public Access Plan. All the authors have no competing financial interests.

References

1. U. Wietelmann and R. J. Bauer, 'Lithium and Lithium Compounds', in "Ullmann's Encyclopedia of Industrial Chemistry", Wiley-VCH Verlag GmbH & Co KGaA, Weinheim, Germany, 2000
2. A. Somrani, A. H. Hamzaoui and M. Pontie, *Desalination*, 2013, **317**, 184
3. S. Ziemann, M. Weil and L. Schebek, *Resour. Conserv. Recycl.*, 2012, **63**, 26
4. C. Grosjean, P. H. Miranda, M. Perrin and P. Poggi, *Renew. Sustain. Energy Rev.*, 2012, **16**, (3), 1735
5. G. Yang, H. Shi, W. Liu, W. Xing and N. Xu, *Chin. J. Chem. Eng.*, 2011, **19**, (4), 586
6. P. K. Choubey, M. Kim, R. R. Srivastava, J. Lee and J.-Y. Lee, *Min. Eng.*, 2016, **89**, 119
7. P. Meshram, B. D. Pandey and T. R. Mankhand, *Hydrometallurgy*, 2014, **150**, 192
8. J. W. An, D. J. Kang, K. T. Tran, M. J. Kim, T. Lim and T. Tran, *Hydrometallurgy*, 2012, **117–118**, 64
9. D. A. Boryta, T. F. Kullberg and A. M. Thurston, Cemetal Foote Corp, 'Production of Lithium Compounds Directly from Lithium Containing Brines', *US Patent Appl.*, 2011/0,123,427
10. S.-Y. Sun, X. Song, Q.-H. Zhang, J. Wang and J.-G. Yu, *Adsorption*, 2011, **17**, (5), 881
11. M. J. Ariza, D. J. Jones, J. Rozière, R. Chitrakar and K. Ooi, *Chem. Mater.*, 2006, **18**, (7), 1885
12. M. M. Thackeray, P. J. Johnson, L. A. de Picciotto, P. G. Bruce and J. B. Goodenough, *Mater. Res. Bull.*, 1984, **19**, (2), 179
13. Q. Feng, Y. Miyai, H. Kanoh and K. Ooi, *Langmuir*, 1992, **8**, (7), 1861
14. Q.-H. Zhang, S.-P. Li, S.-Y. Sun, X.-S. Yin and J.-G. Yu, *Chem. Eng. Sci.*, 2010, **65**, (1), 169
15. Q.-H. Zhang, S. Sun, S. Li, H. Jiang and J.-G. Yu, *Chem. Eng. Sci.*, 2007, **62**, (18–20), 4869
16. Q. Feng, Y. Higashimoto, K. Kajiyoshi and K. Yanagisawa, *J. Mater. Sci. Lett.*, 2001, **20**, (3), 269
17. C. Özgür, *Solid State Ionics*, 2010, **181**, (31–32), 1425
18. L. Li, W. Qu, F. Liu, T. Zhao, X. Zhang, R. Chen and F. Wu, *Appl. Surf. Sci.*, 2014, **315**, 59
19. R. Chitrakar, Y. Makita, K. Ooi and A. Sonoda, *Chem. Lett.*, 2012, **41**, (12), 1647
20. R. Chitrakar, H. Kanoh, Y. Miyai and K. Ooi, *Ind.*

- Eng. Chem. Res.*, 2001, **40**, (9), 2054
21. L. Liu, H. Zhang, Y. Zhang, D. Cao and X. Zhao, *Colloids Surf. A: Physiochem. Eng. Aspects*, 2015, **468**, 280
 22. X. Shi, D. Zhou, Z. Zhang, L. Yu, H. Xu, B. Chen and X. Yang, *Hydrometallurgy*, 2011, **110**, (1–4), 99
 23. R. Chitrakar, H. Kanoh, Y. Miyai and K. Ooi, *Chem. Mater.*, 2000, **12**, (10), 3151
 24. J.-L. Xiao, S.-Y. Sun, J. Wang, P. Li and J.-G. Yu, *Ind. Eng. Chem. Res.*, 2013, **52**, (34), 11967
 25. S.-Y. Sun, J.-L. Xiao, J. Wang, X. Song and J.-G. Yu, *Ind. Eng. Chem. Res.*, 2014, **53**, (40), 15517
 26. R. Chitrakar, K. Sakane, A. Umeno, S. Kasaishi, N. Takagi and K. Ooi, *J. Solid State Chem.*, 2002, **169**, (1), 66
 27. X. Yang, H. Kanoh, W. Tang and K. Ooi, *J. Mater. Chem.*, 2000, **10**, (8), 1903
 28. K. Ooi, Y. Makita, A. Sonoda, R. Chitrakar, Y. Tasaki-Handa and T. Nakazato, *Chem. Eng. J.*, 2016, **288**, 137
 29. H.-J. Hong, I.-S. Park, T. Ryu, J. Ryu, B.-G. Kim and K.-S. Chung, *Chem. Eng. J.*, 2013, **234**, 16
 30. T. Ryu, Y. Haldorai, A. Rengaraj, J. Shin, H.-J. Hong, G.-W. Lee, Y.-K. Han, Y. S. Huh and K.-S. Chung, *Ind. Eng. Chem. Res.*, 2016, **55**, (26), 7218
 31. K. S. Chung, J. C. Lee, E. J. Kim, K. C. Lee, Y. S. Kim and K. Ooi, *Mater. Sci. Forum*, 2004, **449–452**, 277
 32. Y. Miyai, K. Ooi, T. Nishimura and J. Kumamoto, *Bull. Soc. Sea Water Sci., Jpn.*, 1994, **48**, (6), 411
 33. L. Wang, W. Ma, R. Liu, H. Y. Li and C. G. Meng, *Solid State Ionics*, 2006, **177**, (17–18), 1421
 34. J. C. Hunter, *J. Solid State Chem.*, 1981, **39**, (2), 142
 35. G. Xiao, K. Tong, L. Zhou, J. Xiao, S. Sun, P. Li and J. Yu, *Ind. Eng. Chem. Res.*, 2012, **51**, (33), 10921
 36. L.-W. Ma, B.-Z. Chen, Y. Chen and X.-C. Shi, *Micropor. Mesopor. Mater.*, 2011, **142**, (1), 147
 37. R. Chitrakar, H. Kanoh, Y. Makita, Y. Miyai and K. Ooi, *J. Mater. Chem.*, 2000, **10**, (10), 2325
 38. L. Croguennec, P. Deniard, R. Brec and A. Lecerf, *J. Mater. Chem.*, 1997, **7**, (3), 511
 39. L. Tian, W. Ma and M. Han, *Chem. Eng. J.*, 2010, **156**, (1), 134
 40. Q. Feng, Y. Miyai, H. Kanoh and K. Ooi, *Chem. Mater.*, 1993, **5**, (3), 311
 41. R. Chitrakar, Y. Makita, K. Ooi and A. Sonoda, *Ind. Eng. Chem. Res.*, 2014, **53**, (9), 3682
 42. Y. Miyai, K. Ooi and S. Katoh, *Sep. Sci. Technol.*, 1988, **23**, (1–3), 179
 43. R. Chitrakar, Y. Makita, K. Ooi and A. Sonoda, *Dalton Trans.*, 2014, **43**, (23), 8933
 44. L. Zhang, D. Zhou, G. He, F. Wang and J. Zhou, *Mater. Lett.*, 2014, **135**, 206
 45. X. Shi, Z. Zhang, D. Zhou, L. Zhang, B. Chen and L. Yu, *Trans. Nonferrous Met. Soc. China*, 2013, **23**, (1), 253
 46. C. P. Lawagon, G. M. Nisola, J. Mun, A. Tron, R. E. C. Torrejos, J. G. Seo, H. Kim and W.-J. Chung, *J. Ind. Eng. Chem.*, 2016, **35**, 347
 47. D. Tang, D. Zhou, J. Zhou, P. Zhang, L. Zhang and Y. Xia, *Hydrometallurgy*, 2015, **157**, 90
 48. S. Wang, P. Li, W. Cui, H. Zhang, H. Wang, S. Zheng and Y. Zhang, *RSC Adv.*, 2016, **6**, (104), 102608
 49. L. Zhang, D. Zhou, Q. Yao and J. Zhou, *Appl. Surf. Sci.*, 2016, **368**, 82
 50. A. Deptuła, M. Brykała, W. Łada, T. Olczak, B. Sartowska, A. G. Chmielewski, D. Wawszczak and C. Alvani, *Fusion Eng. Des.*, 2009, **84**, (2–6), 681
 51. C.-L. Yu, F. Wang, S.-Y. Cao, D.-P. Gao, H.-B. Hui, Y.-Y. Guo and D.-Y. Wang, *Dalton Trans.*, 2015, **44**, (35), 15721
 52. G. He, L. Zhang, D. Zhou, Y. Zou and F. Wang, *Ionics*, 2015, **21**, (8), 2219
 53. L. A. Limjuco, G. M. Nisola, C. P. Lawagon, S.-P. Lee, J. G. Seo, H. Kim and W.-J. Chung, *Colloids Surf. A: Physiochem. Eng. Aspects*, 2016, **504**, 267
 54. G.-N. Zhu, Y.-G. Wang and Y.-Y. Xia, *Energy Environ. Sci.*, 2012, **5**, (5), 6652
 55. J. P. Thiel, C. K. Chiang and K. R. Poeppelmeier, *Chem. Mater.*, 1993, **5**, (3), 297
 56. A. M. Fogg, A. J. Freij and G. M. Parkinson, *Chem. Mater.*, 2002, **14**, (1), 232
 57. A. V. Besserguenev, A. M. Fogg, R. J. Francis, S. J. Price, D. O'Hare, V. P. Isupov and B. P. Tolochko, *Chem. Mater.*, 1997, **9**, (1), 241
 58. A. M. Fogg and D. O'Hare, *Chem. Mater.*, 1999, **11**, (7), 1771
 59. G. R. Williams and D. O'Hare, *J. Phys. Chem. B*, 2006, **110**, (22), 10619
 60. S.-L. Wang, C.-H. Lin, Y.-Y. Yan and M. K. Wang, *Appl. Clay Sci.*, 2013, **72**, 191
 61. J. Qu, X. He, B. Wang, L. Zhong, L. Wan, X. Li, S. Song and Q. Zhang, *Appl. Clay Sci.*, 2016, **120**, 24
 62. J. M. Lee and W. C. Bauman, The Dow Chemical Company, 'Recovery of Lithium from Brines', *US*

- Patent Appl.* 1979/4,159,311
63. W. C. Bauman and J. L. Burba III, FMC Corp, 'Composition for the Recovery of Lithium Values from Brine and Process of Making/Using Said Composition', *US Patent*, 6,280,693; 2001
 64. N. P. Kotsupalo, A. D. Ryabtsev, I. A. Poroshina, A. A. Kurakov, E. V. Mamylova, L. T. Menzheres and M. A. Korchagin, *Russ. J. Appl. Chem.*, 2013, **86**, (4), 482
 65. J. L. Burba III, R. F. Stewart, B. E. Viani, S. Harrison, C. E. Vogdes and J. G. S. Lahlouh, Simbol Inc, 'Improved Sorbent for Lithium Extraction', *World Patent Appl.*, 2015/171,109
 66. X. Wen, P. Ma, C. Zhu, Q. He and X. Deng, *Sep. Purif. Technol.*, 2006, **49**, (3), 230
 67. Q. Bi, Z. Zhang, C. Zhao and Z. Tao, *Water Sci. Technol.*, 2014, **70**, (10), 1690
 68. S.-Y. Sun, L.-J. Cai, X.-Y. Nie, X. Song and J.-G. Yu, *J. Water Process Eng.*, 2015, **7**, 210
 69. W. Li, C. Shi, A. Zhou, X. He, Y. Sun and J. Zhang, *Sep. Purif. Technol.*, 2017, **186**, 233
 70. Z. Zhao, X. Si, X. Liu, L. He and X. Liang, *Hydrometallurgy*, 2013, **133**, 75
 71. X. Liu, X. Chen, Z. Zhao and X. Liang, *Hydrometallurgy*, 2014, **146**, 24
 72. X. Liu, X. Chen, L. He and Z. Zhao, *Desalination*, 2015, **376**, 35
 73. T. Hoshino, *Fusion Eng. Des.*, 2013, **88**, (11), 2956
 74. T. Hoshino, *Desalination*, 2015, **359**, 59
 75. T. Hoshino, *Desalination*, 2013, **317**, 11
 76. Z. Ji, Q. Chen, J. Yuan, J. Liu, Y. Zhao and W. Feng, *Sep. Purif. Technol.*, 2017, **172**, 168
 77. P. Ma, X. D. Chen and M. M. Hossain, *Sep. Sci. Technol.*, 2000, **35**, (15), 2513
 78. L. Xing, J. Song, Z. Li, J. Liu, T. Huang, P. Dou, Y. Chen, X.-M. Li and T. He, *J. Membrane Sci.*, 2016, **520**, 596
 79. J. Song, X.-M. Li, Y. Zhang, Y. Yin, B. Zhao, C. Li, D. Kong and T. He, *J. Membrane Sci.*, 2014, **471**, 372
 80. Y. Guo, Y. Ying, Y. Mao, X. Peng and B. Chen, *Angew. Chem.*, 2016, **128**, (48), 15344
 81. A. Umeno, Y. Miyai, N. Takagi, R. Chitrakar, K. Sakane and K. Ooi, *Ind. Eng. Chem. Res.*, 2002, **41**, (17), 4281
 82. K.-S. Chung, J.-C. Lee, W.-K. Kim, S. B. Kim and K. Y. Cho, *J. Membrane Sci.*, 2008, **325**, (2), 503
 83. W.-J. Chung, R. E. C. Torrejos, M. J. Park, E. L. Vivas, L. A. Limjuco, C. P. Lawagon, K. J. Parohinog, S.-P. Lee, H. K. Shon, H. Kim and G. M. Nisola, *Chem. Eng. J.*, 2017, **309**, 49
 84. M. J. Park, G. M. Nisola, E. L. Vivas, L. A. Limjuco, C. P. Lawagon, J. G. Seo, H. Kim, H. K. Shon and W.-J. Chung, *J. Membrane Sci.*, 2016, **510**, 141
 85. R. Bhave, V. Deshmane and D. Kim, 'Selective Recovery of Lithium from Geothermal Brine Using Novel Mixed Matrix Membranes Supported on Hollow Fiber and Inorganic Supports', 2018, *in preparation*
 86. J. A. Epstein, E. M. Feist, J. Zmora and Y. Marcus, *Hydrometallurgy*, 1981, **6**, (3-4), 269
 87. D. A. Lee, W. L. Taylor, W. J. McDowell and J. S. Drury, *J. Inorg. Nucl. Chem.*, 1968, **30**, (10), 2807
 88. C. Shi, Y. Jing and Y. Jia, *J. Mol. Liq.*, 2016, **215**, 640
 89. C. Shi, Y. Jing and Y. Jia, *Russ. J. Phys. Chem. A*, 2017, **91**, (4), 692
 90. B. El-Eswed, M. Sunjuk, Y. S. Al-Degs and A. Shtaiwi, *Separ. Sci. Technol.*, 2014, **49**, (9), 1342
 91. E. G. Pinna, M. C. Ruiz, M. W. Ojeda and M. H. Rodriguez, *Hydrometallurgy*, 2017, **167**, 66
 92. G. P. Nayaka, J. Manjanna, K. V. Pai, R. Vadavi, S. J. Keny and V. S. Tripathi, *Hydrometallurgy*, 2015, **151**, 73
 93. M. Joulié, E. Billy, R. Laucournet and D. Meyer, *Hydrometallurgy*, 2017, **169**, 426
 94. S.-H. Joo, D. ju Shin, C. Oh, J.-P. Wang, G. Senanayake and S. M. Shin, *Hydrometallurgy*, 2016, **159**, 65
 95. C. K. Lee and K.-I. Rhee, *J. Power Sources*, 2002, **109**, (1), 17
 96. J. Xu, H. R. Thomas, R. W. Francis, K. R. Lum, J. Wang and B. Liang, *J. Power Sources*, 2008, **177**, (2), 512
 97. M. Contestabile, S. Panero and B. Scrosati, *J. Power Sources*, 2001, **92**, (1-2), 65
 98. S. Castillo, F. Ansart, C. Laberty-Robert and J. Portal, *J. Power Sources*, 2002, **112**, (1), 247
 99. D. C. R. Espinosa, A. M. Bernardes and J. A. S. Tenório, *J. Power Sources*, 2004, **135**, (1-2), 311
 100. P. Zhang, T. Yokoyama, O. Itabashi, T. M. Suzuki and K. Inoue, *Hydrometallurgy*, 1998, **47**, (2-3), 259
 101. L. Li, J. Ge, F. Wu, R. Chen, S. Chen and B. Wu, *J. Hazard. Mater.*, 2010, **176**, (1-3), 288
 102. J. Nan, D. Han and X. Zuo, *J. Power Sources*, 2005, **152**, 278
 103. B. Swain, J. Jeong, J. Lee, G.-H. Lee and J.-S. Sohn, *J. Power Sources*, 2007, **167**, (2), 536
 104. J. Ordoñez, E. J. Gago and A. Girard, *Renew. Sustain. Energy Rev.*, 2016, **60**, 195
 105. Y. Guo, F. Li, H. Zhu, G. Li, J. Huang and W. He,

- Waste Manage.*, 2016, **51**, 227
106. S. P. Barik, G. Prabakaran and B. Kumar, *Waste Manage.*, 2016, **51**, 222
107. X. Chen, H. Ma, C. Luo and T. Zhou, *J. Hazard. Mater.*, 2017, **326**, 77
108. L.-P. He, S.-Y. Sun, X.-F. Song and J.-G. Yu, *Waste Manage.*, 2017, **64**, 171
109. L. Li, E. Fan, Y. Guan, X. Zhang, Q. Xue, L. Wei, F. Wu and R. Chen, *ACS Sustainable Chem. Eng.*, 2017, **5**, (6), 5224
110. J. Xiao, J. Li and Z. Xu, *Environ. Sci. Technol.*, 2017, **51**, (20), 11960

The Authors



Dr Ling Li obtained her PhD in Materials Science and Engineering from the University of Tennessee, Knoxville, USA, in 2015. Then she worked as a Postdoctoral Fellow at Oak Ridge National Laboratory (ORNL), USA, from 2015 to 2017. She is currently a Materials Scientist at Magic Leap Inc. in Austin, Texas, USA.



Dr Vishwanath G. Deshmene is a Postdoctoral Research Associate in the Materials Science & Technology Division of ORNL. He earned his PhD degree with Chemical Engineering major from North Carolina A&T State University, Greensboro, USA, in 2012 and Master's degree in Chemical Engineering from the Institute of Chemical Technology, Mumbai, India, in 2007. He joined ORNL in 2016 after completing his postdoctoral research at North Carolina A&T State University. He has more than seven years of research and development experience in catalysis and membrane separations and one year of industrial process engineering experience. He has more than 16 peer-reviewed publications with 450+ citations.



Dr Mariappan Parans Paranthaman is a Corporate Fellow and a Group Leader at ORNL. He is a fellow of the National Academy of Inventors, the American Association for the Advancement of Science (AAAS), American Ceramic Society, ASM International and the Institute of Physics, London, UK. He earned his PhD degree in Chemistry from the Indian Institute of Technology, Madras, India, in 1988. After completing his postdoctoral research at the University of Texas at Austin and the University of Colorado, Boulder, USA, he joined ORNL in May 1993. He has authored or co-authored more than 400 journal publications with an "h-index" of 59 (Google scholar citation) and issued 37 US Patents related to superconductivity, energy storage and solar cells.



Dr Ramesh Bhawe is a Distinguished Staff and a Team Leader at ORNL. He earned his PhD degree in Chemical Engineering from the University of Bombay, India. After completing his postdoctoral research at the Stevens Institute of Technology, Hoboken, New Jersey, USA, he joined industry and worked for Alcoa, US Filter and Pall Corporation in the USA for a span of over 21 years before joining ORNL in early 2008. He has authored or co-authored more than 50 journal publications and has 12 issued US Patents related to membrane separations covering a wide range of applications.



Dr Bruce A. Moyer is a Corporate Fellow at ORNL, leading the Chemical Separations Group. He received his BS degree in chemistry from Duke University, USA, in 1974 and his PhD in inorganic chemistry from the University of North Carolina at Chapel Hill, USA, in 1979. In addition to leading programmes in fundamentals of extraction, nuclear-fuel-cycle separations and critical materials, he led the chemical development of the caustic side solvent extraction process in use for caesium removal from millions of gallons of nuclear waste. Dr Moyer is Co-editor of the journal *Solvent Extraction and Ion Exchange* and the book series *Ion Exchange and Solvent Extraction*.



Dr Stephen Harrison is the Chief Technology Officer (CTO) of Alger Alternative Energy, LLC, USA. Previously, he served as the CTO of Simbol, Inc, USA. Dr Harrison led Simbol's development of Li, Mn and Zn extraction for existing geothermal power plants and invented the process used by Limtech, Inc, USA, for the production of high-purity lithium carbonate. He has more than 40 patents and 12 publications. Dr Harrison has a Chemistry degree from Loughborough University, UK, and a PhD in Chemical Engineering from the University of Newcastle upon Tyne, UK. He has spent many years developing sustainable chemical processes firstly with Hydro-Quebec, Canada, and more recently in California with AIC Labs Inc, USA.